

First-principles calculations of the high-temperature phase transformation in yttrium tantalateJing Feng,¹ Samuel Shian,¹ Bing Xiao,² and David R. Clarke^{1,*}¹*School of Engineering and Applied Sciences, Harvard University, Cambridge, Massachusetts 02138, USA*²*Departments of Physics, College of Science and Engineering, Temple University, Philadelphia, Pennsylvania 19122, USA*

(Received 23 April 2014; revised manuscript received 18 August 2014; published 2 September 2014)

The high-temperature phase transition between the tetragonal (scheelite) and monoclinic (fergusonite) forms of yttrium tantalite (YTaO_4) has been studied using a combination of first-principles calculations and a Landau free-energy expansion. Calculations of the Gibbs free energies show that the monoclinic phase is stable at room temperature and transforms to the tetragonal phase at 1430°C , close to the experimental value of $1426 \pm 7^\circ\text{C}$. Analysis of the phonon modes as a function of temperature indicate that the transformation is driven by softening of transverse acoustic modes with symmetry E_u in the Brillouin zone center rather than the Raman-active B_g mode. Landau free-energy expansions demonstrate that the transition is second order and, based on the fitting to experimental and calculated lattice parameters, it is found that the transition is a proper rather than a pseudoproper type. Together these findings are consistent with the transition being ferroelastic.

DOI: [10.1103/PhysRevB.90.094102](https://doi.org/10.1103/PhysRevB.90.094102)

PACS number(s): 87.15.Zg, 77.80.bn, 71.15.Mb, 68.35.Gy

I. INTRODUCTION

A number of compounds are now known to undergo a ferroelastic phase transition [1–5] on cooling or in response to an applied stress. They share the characteristics of being second order with a continuous change in the unit cell volume at the transition. Furthermore, group theory analysis indicates that the high and low symmetry phases are connected by an irreducible representation in the Brillouin zone center. In addition, an intriguing feature of materials that can undergo a ferroelastic phase transition is that they are capable of exhibiting toughening if the stress is sufficiently high to trigger the transformation from one variant to another [6,7]. This occurs, for instance, in yttria-stabilized zirconia [7–10]. In this oxide material, the high-temperature cubic phase undergoes a ferroelastic transformation to crystallographically equivalent tetragonal variants, which can be switched by an applied stress, dissipating energy and thereby producing toughening. This is believed to be the basis for the unusually high fracture toughness of YSZ thermal barrier coating at elevated temperatures [7]. In the search for other oxides capable of ferroelastic toughening, we have been studying the transformations in YTaO_4 to determine whether it, too, exhibits a ferroelastic phase transition. From *in situ* x-ray diffraction experiments, the high symmetry scheelite- YTaO_4 ($I_{41/a}$) is stabilized over monoclinic fergusonite- YTaO_4 ($C_{2/c}$) phase above $1426 \pm 7^\circ\text{C}$. However, the detailed transition mechanism in the YTaO_4 system has not been established and this motivates the first-principles calculations presented here.

One of the earliest studies to understand the mechanism underlying ferroelastic phase transitions using first-principles methods was reported by Carpenter and co-workers in crystalline silica (SiO_2) [11]. The tetragonal stishovite (P_{42}/mmm) to orthorhombic CaCl_2 type SiO_2 ($Pnmm$) is rationalized as a prototypical pseudoproper ferroelastic transition under pressure. Both experiments and theoretical calculations confirmed that the transition is driven by the softening of the zone-center

B_{1g} optical mode, a Raman-active mode in the tetragonal-stishovite phase. In addition, the coupling between B_{1g} optical mode and the transverse acoustic modes results in nonlinear variations of the elastic constants as a function of pressure. In Refs. [11–14], expressions for the Landau free-energy expansion for the high symmetry stishovite phase were successfully derived and applied to explain the observed spontaneously macroscopic strains and elastic behaviors. The transformation under pressure of another oxide, the ScVO_4 compound, was studied by Panchal *et al.* [15] by Raman scattering and density-functional perturbation theory (DFPT) calculations. They found that the scheelite ($I_{41/a}$)-to-fergusonite (I_2/a) phase transition in this oxide was a displacive second-order ferroelastic transition and occurred at 9 GPa. However, the softening of the B_{1g} mode in the scheelite phase, which was assumed to be the driving force for phase transition, was not detected by Raman scattering. There is also evidence that the ferroelastic phase transition can only be triggered by the softening of transverse acoustic modes in the Brillouin zone. For instance, Dove [16] and collaborators found that the ferroelastic transitions in $(\text{Na,K})\text{AlSi}_3\text{O}_8$ and $(\text{Sr,Ca})\text{Al}_2\text{Si}_2\text{O}_8$ feldspar solid solutions as a function of pressure are indeed driven by the vanishing of a combination of transverse acoustic elastic constants and without softening of any optical modes. Furthermore, other ferroelastic phase transitions, such as the temperature induced transitions in $\text{Li}_2\text{TiGeO}_5$ [17] and CaCl_2 [18] and pressure induced transitions in RuO_2 [19] and SnO_2 [20], have been successfully studied by first-principles calculations, to get the mechanism of the ferroelastic phase transitions. These studies indicate that the transformation is associated with a softening mode.

Figure 1 shows the crystal structure of high-temperature tetragonal (scheelite) and low-temperature monoclinic (fergusonite) phases of YTaO_4 . At ambient conditions, YTaO_4 exists in the fergusonite monoclinic structure (space group $I_{12}/a1$, No. 15, point group C_{2h}^6). With increasing the temperature, the phase changes to the scheelite tetragonal structure (space group I_{41}/a , No. 88, point group C_{4h}^6). Both phases contain four formula units per crystal cell with TaO_4 tetrahedra bonded to Y and O ions as shown. Crystallographically, the two structures are related by a 90° rotation around the common \mathbf{a} axis, given

*Corresponding author: clarke@seas.harvard.edu

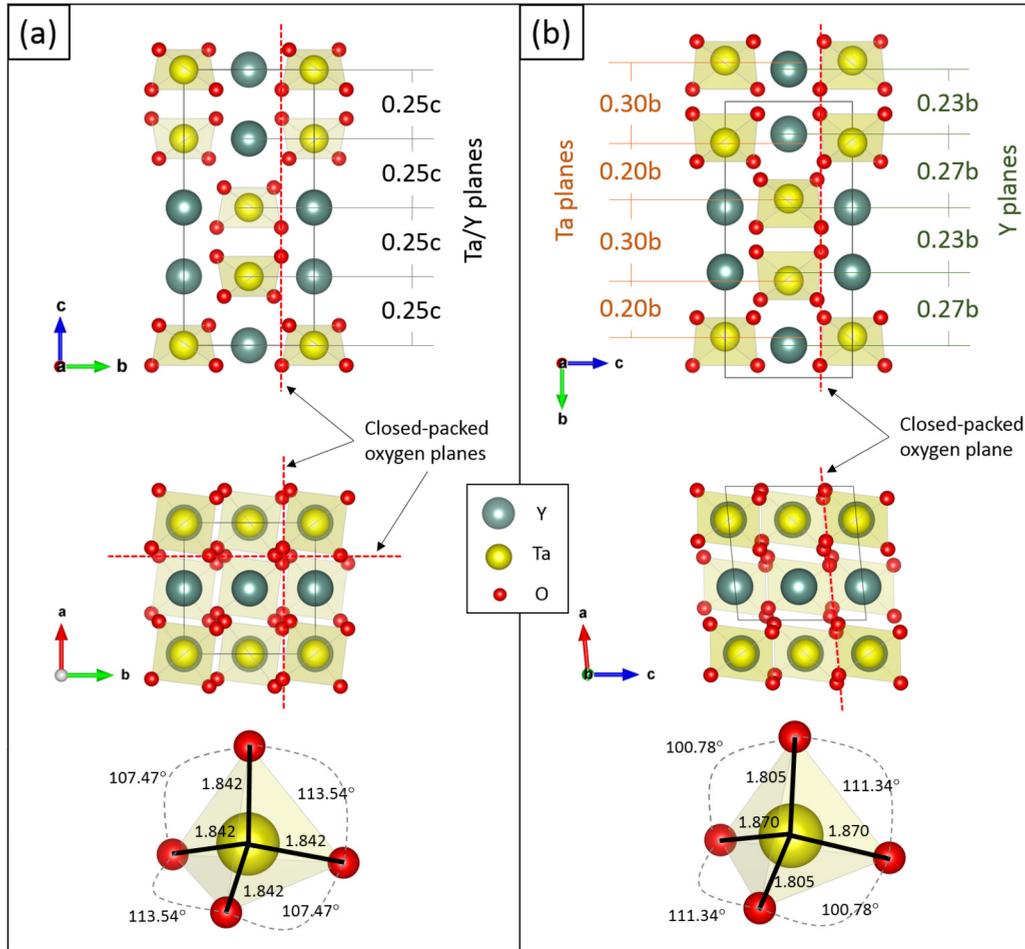


FIG. 1. (Color online) Projections of (a) the tetragonal structure at 1475 °C (space group $I4_1/a$, No. 88, point group C_{4h}^6) and (b) the monoclinic structure at 20 °C (space group $I_{12}/a1$, No. 15, point group C_{2h}^6) of $YTaO_4$. Comparison of the positions of the ions in the a projection (top row) indicates that in the tetragonal phase both the Ta and Y atoms lie in the same a - b plane and the planes are equidistant along the c axis. In the monoclinic phase, however, each Ta and Y atoms are slightly in different planes and each plane is not equidistant along the longest axis (b axis of monoclinic). In addition, each Ta-O bond in the TaO_4 tetrahedra has equal length in the tetragonal structure, whereas they have slightly different lengths in the monoclinic structure (bottom row).

by the matrix

$$\begin{pmatrix} a_m \\ b_m \\ c_m \end{pmatrix} = \begin{pmatrix} 0 & 1 & -1 \\ 0 & 1 & 0 \\ 1 & 0 & 0 \end{pmatrix} \begin{pmatrix} a_t \\ b_t \\ c_t \end{pmatrix}. \quad (1)$$

In this orientation, the C_2 rotational axis in the $[001]$ direction of the tetragonal phase is parallel to the b direction in the monoclinic phase.

In this work we report the results of tetragonal-to-monoclinic phase transition in $YTaO_4$ by combining the theoretical calculations with the high-temperature x-ray diffraction measurements. The Landau free-energy expansion for the tetragonal scheelite- $YTaO_4$ has been derived assuming, initially, that it undergoes pseudoproper transformation and the corresponding spontaneously macroscopic strains were obtained. Using the DFPT, the phonon spectra and the soft modes were discussed. Our results indicate that the phase transition in the $YTaO_4$ system is driven by the softening

of transverse acoustic modes and that the transformation is a proper type, rather than a pseudoproper type initially assumed.

II. LANDAU FREE-ENERGY EXPANSION

In Landau theory, a second-order phase transition is described using group theory, in which the excess free energy of the crystals is expanded as a function of order parameter Q near the transition temperature. The order parameter is zero in the high symmetry phase, and increases as this symmetry is progressively “broken” in the low symmetry phase. For a temperature-dependent phase transition, the order parameter is set as unity at absolute zero. The Landau free-energy G' is the difference in free energy between the low symmetry phase G and the high symmetry phase G_o [21]. In ferroelastic crystals, the transformation introduces lattice distortions, which can be described using spontaneous strains. The elastic energy G_e can be directly related to the changes in the lattice parameters, which are measurable. Furthermore, in a pseudoproper

transformation, the spontaneous strains do not coincide with the order parameter, instead, they interact through coupling coefficient λ [22] and contribute to the coupling free energy G_c . Therefore, the Landau free energy can be written as the sum of the three energies [23–26]:

$$G' = G - G_0 = G_Q + G_e + G_c, \quad (2a)$$

where

$$G_Q = \frac{1}{2}a'(T - T_C)Q^2 + \frac{1}{4}b'Q^4, \quad (2b)$$

$$G_e = \frac{1}{2} \sum_{i,j=1,3} c_{ij}^0 e_i e_j + \frac{1}{2} \sum_{k=4,6} c_{kk}^0 e_k^2, \quad (2c)$$

$$G_c = \sum_s \lambda_s e_s Q + \sum_{ns} \lambda_{ns} e_{ns} Q^2. \quad (2d)$$

The standard Landau expansion G_Q is limited to fourth order, where a' and b' are coefficients in the series expansion. The elastic energy G_e is calculated from the strains and the elastic constants. The coupling energy G_c is limited to the second order and since the symmetry-breaking strain are directly proportional to the order parameter, the sum of their exponents should also follow Landau's expansion (only two are used here). Thus, the coupling between the order parameter Q and spontaneous strains e can be categorized into symmetry-breaking strain (subscript s) and nonsymmetry-breaking strain (subscript ns) with bilinear and linear-quadratic couplings with the order parameter, respectively. Note that for the high symmetry phase, all the spontaneous strains and the Q vanish and the Landau free energy is simply zero.

To expand the above equation for YTaO₄, the relation between the tetragonal and the monoclinic lattice parameters must be formulated using an irreducible representation and then the spontaneous strains can be derived. The crystal symmetries of the high-temperature tetragonal and low-temperature monoclinic phases of YTaO₄ are reported to be (I_{41}/a) and (C_2/c), respectively [27–29]. In this transformation, the spontaneous strains can be expressed in terms of the lattice parameters of both the monoclinic and tetragonal phases using the following [30]:

$$\begin{aligned} e_1 &= \frac{c_M \sin \beta}{a_T} - 1, & e_2 &= \frac{a_M}{a_T} - 1, \\ e_3 &= \frac{b_M}{c_T} - 1, & e_4 &= e_5 = 0, & e_6 &= -\frac{c_M \cos \beta}{2a_T}. \end{aligned} \quad (3)$$

Analysis of the possible lattice correspondences between these structures using the group theory ISOTROPY code [<http://stokes.byu.edu/iso/isotropy.php>] indicate that they can be expressed in terms of symmetry-breaking strain based on the B_{1g} symmetry in the Brillouin zone. The symmetry-breaking strains are $e_{xx} - e_{yy}$ and e_{xy} (or $e_1 - e_2$ and e_6 in the Voigt notation) relative to the high-temperature tetragonal phase. They can be defined in terms of the crystallographic coordinates relative to a Cartesian coordinate system for the monoclinic to tetragonal phase transition shown in Fig. 2. These two strains are the symmetry adaptive strains which determine the low symmetry phase completely. The nonsymmetry-breaking strains anticipated for the phase

transition are $e_1 + e_2$ and e_3 with A_{1g} symmetry in the BZ center. Note that the transformation does not depend on the volume strain $e_1 + e_2 + e_3$.

From these considerations, Eqs. (2a)–(2d) can be expressed as follows:

$$\begin{aligned} G'(Q, e_i) &= \frac{1}{2}a'(T - T_C)Q^2 + \frac{1}{4}b'Q^4 + \lambda_1(e_1 + e_2)Q^2 \\ &+ \lambda_2 e_3 Q^2 + \lambda_3(e_1 - e_2)Q + \lambda_4 e_6 Q \\ &+ \frac{1}{4}(c_{11}^0 + c_{12}^0)(e_1 + e_2)^2 \\ &+ \frac{1}{4}(c_{11}^0 - c_{12}^0)(e_1 - e_2)^2 \\ &+ c_{13}^0(e_1 + e_2)e_3 + \frac{1}{2}c_{33}^0 e_3^2 + \frac{1}{2}c_{66}^0 e_6^2. \end{aligned} \quad (4)$$

The normal elastic constants involved in the phase transitions are given for the monoclinic phase as c_{11}^0 , c_{12}^0 , c_{13}^0 , c_{33}^0 , and c_{66}^0 . Exact relationships between the strains and Q can be calculated by invoking equilibrium, i.e., the first derivative of the Landau free energy with respect to both the order parameter and spontaneous strains ($e_1 - e_2$, $e_1 + e_2$, and e_6) are zero:

$$\begin{aligned} \frac{\partial G'}{\partial Q} &= 0, & \frac{\partial G'}{\partial(e_1 - e_2)} &= 0, \\ \frac{\partial G'}{\partial(e_1 + e_2)} &= 0, & \frac{\partial G'}{\partial e_6} &= 0. \end{aligned} \quad (5)$$

They are found to be

$$e_1 + e_2 = \frac{2(\lambda_2 c_{13}^0 - \lambda_1 c_{33}^0)}{c_{33}^0(c_{11}^0 + c_{12}^0) - 2c_{13}^0} Q^2, \quad (6)$$

$$e_1 - e_2 = -\frac{2\lambda_3}{c_{11}^0 - c_{12}^0} Q, \quad (7)$$

$$e_3 = \frac{2\lambda_1 c_{13}^0 - \lambda_2(c_{11}^0 + c_{12}^0)}{c_{33}^0(c_{11}^0 + c_{12}^0) - 2c_{13}^0} Q^2, \quad (8)$$

$$e_6 = \frac{-\lambda_4}{c_{66}^0} Q. \quad (9)$$

Later, using strains, defined in Eqs. (3), and calculated from the first-principles lattice parameters together with the computed elastic constants (Table II), the coupling coefficients λ_1 , λ_2 , λ_3 , and λ_4 , were obtained by solving Eqs. (6)–(9).

In turn, the renormalized Landau excess free energy for the monoclinic YTaO₄ phase can be written as

$$G' = \frac{1}{2}a'(T - T_c^*)Q^2 + \frac{1}{4}b^*Q^4, \quad (10)$$

with the renormalized transition temperature T_c^* and coefficient b^* being

$$T_c^* = T_c + \frac{\lambda_3^2}{(c_{11}^0 - c_{12}^0)/2} + \frac{\lambda_4^2}{c_{66}^0}, \quad (11)$$

$$b^* = b' - 2 \frac{2\lambda_1^2 c_{33}^0 + \lambda_3^2 (c_{11}^0 + c_{12}^0) - 4\lambda_1 \lambda_2 c_{13}^0}{c_{33}^0 (c_{11}^0 + c_{12}^0) - 2c_{13}^0}. \quad (12)$$

Consequently, the temperature dependence of the order parameter will be given by

$$Q^2 = \frac{a'}{b^*}(T_c^* - T), \quad T < T_c^*. \quad (13)$$

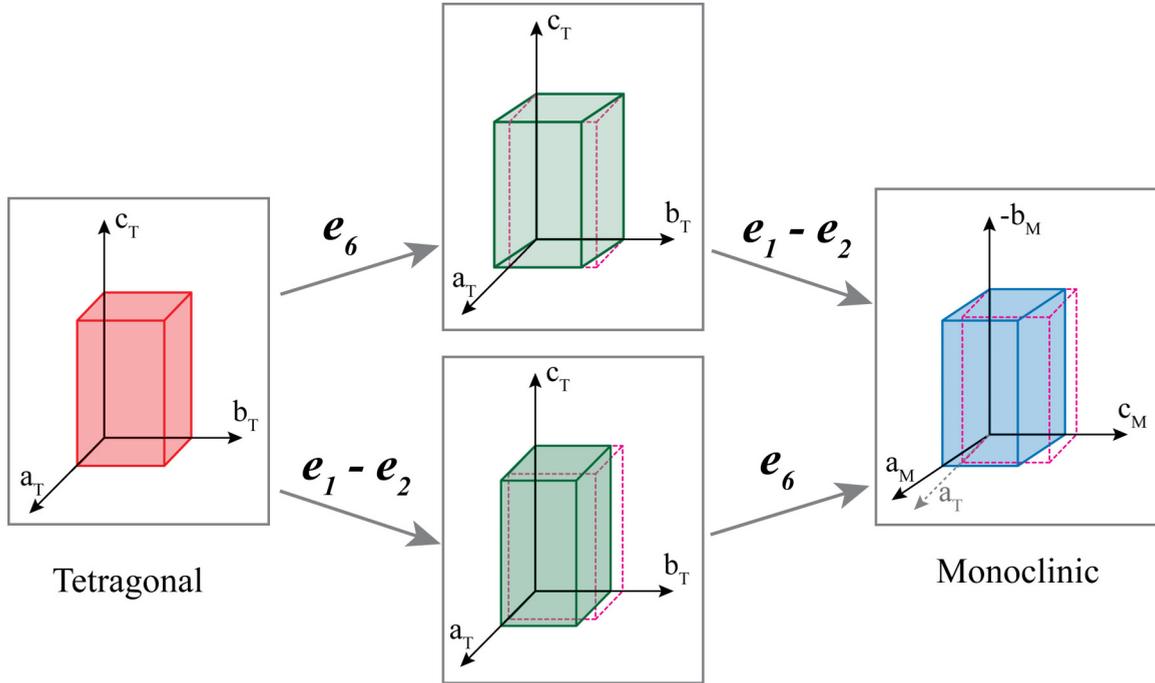


FIG. 2. (Color online) The relations between the symmetry-breaking strains ($e_1 - e_2$ and e_6) and the transformation of the tetragonal to monoclinic unit cells in the Cartesian coordinate system. Note the differences in the axes before and after the transformation.

This has the familiar form of a second order, mean-field transition, with the order parameter dependent of the square root of reduced temperature. However, unlike the tetragonal-to-orthorhombic ferroelastic phase transition in the SiO_2 system [14], for instance, the transition in the YTao_4 system involves an additional dependence on the symmetry-breaking strain e_6 . Specifically, the renormalized transition temperature [Eq. (10)] is dependent on e_6 , whereas the constant b^* is not.

III. CALCULATIONAL METHODS

A. Computational details

The first-principles calculations were based on the density functional theory (DFT) as implemented in CASTEP (Cambridge Serial Total Energy Package) code. The plane wave basis sets were expanded in reciprocal space using a kinetic energy cutoff value of 550 eV. The Monkhorst-Pack method was employed to generate an $8 \times 8 \times 8$ k mesh for the energy integrations in the first irreducible part of the BZ. For the exchange-correlation energy, the generalized gradient approximation (GGA) of the Perdew-Burke-Ernzerhof (PBE) functional was used [31]. The interactions between ionic cores and valence electrons were represented by norm-conserving pseudopotentials. For Y, Ta, and O atoms, the valence electron configurations considered are Y $4d^1 5s^2$, Ta $5d^3 6s^2$, and O $2s^2 2p^4$, respectively. The BFGS (Broyden-Fletcher-Goldfarb-Shannon) optimized method was adopted to obtain the equilibrium crystal structures [32]. The calculations were continued until the total energy changes converged to less than 1.0×10^{-6} eV and the Hellman-Feynman forces acting on distinct atoms converged to less than 0.05 eV/Å.

As part of the calculations we also calculated the ionic and covalent components of the individual bonds based on

Mulliken's population analysis [33]. The Mulliken's charge $Q_m(A)$ of atom A and the overlap population $n_m(AB)$ for the A-B bond are defined in the usual way as follows:

$$Q_m(A) = \sum_k W(k) \sum_{\mu} \sum_{\nu} P_{\mu\nu}(k) S_{\mu\nu}(k), \quad (14)$$

$$n_m(AB) = \sum_k W(k) \sum_{\mu} \sum_{\nu} P_{\mu\nu}(k) S_{\mu\nu}(k),$$

where $P_{\mu\nu}(k)$ and $S_{\mu\nu}(k)$ are the density matrix and the overlap matrix, respectively. W_k is the weight associated with the calculated \mathbf{k} points in the Brillouin zone. The magnitude and sign of $Q_m(A)$ characterizes the ionicity of atom A in the crystal, and $n_m(AB)$ can be used to measure the covalent bonding strength approximately.

Since we are interested in the transformation at finite temperatures and constant pressure, the quasiharmonic approximation (QHA) method [34] was used throughout to calculate the thermodynamic properties of the compounds at finite temperatures [35,36]. These were computed using the GIBBS code with the thermal properties of solids at constant volume calculated in the QHA from their phonon density of states as a function of frequencies. The phonon contribution to the Helmholtz free energy F_{ph} is given by

$$F_{\text{ph}} = \frac{1}{2} \sum_{\mathbf{q}, \nu} \hbar \omega_{\mathbf{q}, \nu} + k_B T \sum_{\mathbf{q}, \nu} \ln \left[1 - \exp \left(-\frac{\hbar \omega_{\mathbf{q}, \nu}}{k_B T} \right) \right], \quad (15)$$

where \mathbf{q} and ν are the wave vector and band index, respectively, $\omega_{\mathbf{q}, \nu}$ is the phonon frequency at \mathbf{q} and ν , and T is the absolute temperature. k_B and \hbar are the Boltzmann constant and the

TABLE I. Lattice parameters and atomic positions of monoclinic and tetragonal YTaO₄ in ground state by experiments (M is at room temperature and T is at 1475 °C) and first-principles calculations (at 0 K). M-YTaO₄ is *C*₂/*c* space group (15) where Y, Ta atoms are both in the 4*e* Wyckoff position, and O atoms are in the 8*f* Wyckoff position. T-YTaO₄ is *I*₄₁/*a* space group (88), where Y, Ta, and O atoms are in the 4*b*, 4*a*, and 16*f* Wyckoff position, respectively.

Phase		<i>a</i>	<i>b</i>	<i>c</i>	β'	<i>V</i>	Atom positions		
		(Å)	(Å)	(Å)	(deg)	(Å ³)	Y	Ta	O
M	expt. ^a	5.2393	10.8939	5.0563	95.52	287.2	(0.25,0.622,0)	(0.25,0.145,0)	(0.090,0.461,0.252) (−0.003,0.717,0.290)
	expt.	5.3253	10.9283	5.0525	95.5	292.7	(0.6175,0,0.5)	(0.1485,0,0.5)	(0.0895,0.45545,0.24453) (−0.02967,0.71743,0.27772)
	calc.	5.1923	10.6639	4.9299	95.46	272.16	(0.25,0.620,0)	(0.25,0.147,0)	(0.091,0.462,0.259) (−0.0143,0.722,0.286)
T	expt.	5.2521		11.15993		307.84	(0,0,0.5)	(0,0,0)	(0.20096,−0.14672,0.07911)
	calc.	5.0985		10.8129		281.08	(0,0,0.6)	(0,0,1)	(0.24075,−0.18263,0.09334)

^aExpt. in Ref. ICSD# 109910.

reduced Planck constant, respectively. The heat capacity C_v and the entropy S at constant volume are given by

$$C_v = \sum_{q,v} k_B \left(\frac{\hbar\omega_{q,v}}{k_B T} \right)^2 \frac{\exp\left(\frac{\hbar\omega_{q,v}}{k_B T}\right)}{\left[\exp\left(\frac{\hbar\omega_{q,v}}{k_B T}\right) - 1\right]^2}, \quad (16)$$

$$S = -k_B \sum_{q,v} \ln \left[1 - \exp\left(-\frac{\hbar\omega_{q,v}}{k_B T}\right) \right] - \frac{1}{T} \sum_{q,v} \frac{\hbar\omega_{q,v}}{\exp\left(\frac{\hbar\omega_{q,v}}{k_B T}\right) - 1}. \quad (17)$$

To compare with experiments, the thermal properties need to be known at constant pressure. These were calculated from the Gibbs free energy G and the F_{ph} using the relationship

$$G(T, P) = \min_V [U(V) + F_{\text{ph}}(T; V) + PV], \quad (18)$$

where V and P are the volume and pressure, respectively, and $U(V)$ is the total energy, including electronic contributions, at constant volume. The Gibbs free energies at finite temperatures were obtained as the minimum values of the thermodynamic functions, and the corresponding equilibrium volumes and isothermal bulk moduli were obtained simultaneously from the equation of states of the YTaO₄ phases. The unit cells used to calculate $U(V)$ and $F_{\text{ph}}(T; V)$ were relaxed by the first-principles calculations under the hydrostatic-stress conditions. Furthermore, to determine the equilibrium volume of the unit cells at different temperatures, we employed the Birch-Murnaghan equation of state [37] to relate the free energy and volume of the tetragonal and monoclinic phases

computed at specific volumes and temperatures:

$$E(V) = E_V + \frac{9V_0 B_0}{16} \left\{ \left[\left(\frac{V_0}{V} \right)^{2/3} - 1 \right]^3 B'_0 + \left[\left(\frac{V_0}{V} \right)^{2/3} - 1 \right]^2 \left[6 - 4 \left(\frac{V_0}{V} \right)^{2/3} \right] \right\}, \quad (19)$$

where $E(V)$ is the internal energy, V_0 is the reference volume, V is the deformed volume, B_0 is the bulk modulus, and B'_0 is the derivative of the bulk modulus with respect to pressure. In this work the calculated bulk modulus of monoclinic and tetragonal phase is 183.7 and 128.9 GPa, respectively. The B'_0 is 4.1 (M-YTaO₄) and 4.2 (T-YTaO₄), and other parameters are tabulated in Tables I and II and the parameters for temperature dependence are shown in Fig. 3. The results of the volume dependent free energies from 200 to 1600 °C at intervals of 200 °C are shown in Fig. 3 together with the Birch-Murnaghan interpolations.

B. Phonon calculations

The phonon spectra of both YTaO₄ phases were calculated using the standard density functional perturbation theory (DFPT) method also implemented in the CASTEP (Cambridge Serial Total Energy Package) code [38–40]. In calculating the phonon dispersion relations and the phonon density of states, a number of approximations were made. First, it was assumed that the mean equilibrium position of each ion is taken to be the positions calculated from the *ab initio* calculations at 0 K. Second, it was assumed that the atomic displacements are small compared to the interatomic distances. This leads to a harmonic approximation which is sufficiently accurate to describe most of the lattice dynamical effects of interest.

TABLE II. Elastic constants (GPa) of monoclinic and tetragonal YTaO₄ calculated by first principles at 0 K.

Phase	c_{11}^0	c_{22}^0	c_{33}^0	c_{44}^0	c_{55}^0	c_{66}^0	c_{12}^0	c_{13}^0	c_{15}^0	c_{23}^0	c_{25}^0	c_{35}^0	c_{46}^0	c_{16}^0	<i>B</i>	<i>G</i>	<i>E</i>
M	354.9	291.9	343	88.1	82.8	73.5	112.3	146.1	1.0	122.5	−20.3	−57.5	−1.6		183.7	63.2	170.1
T	242.6		183.3	29.3		25.4	117.7	70.3						31.8	128.9	52.7	139.1

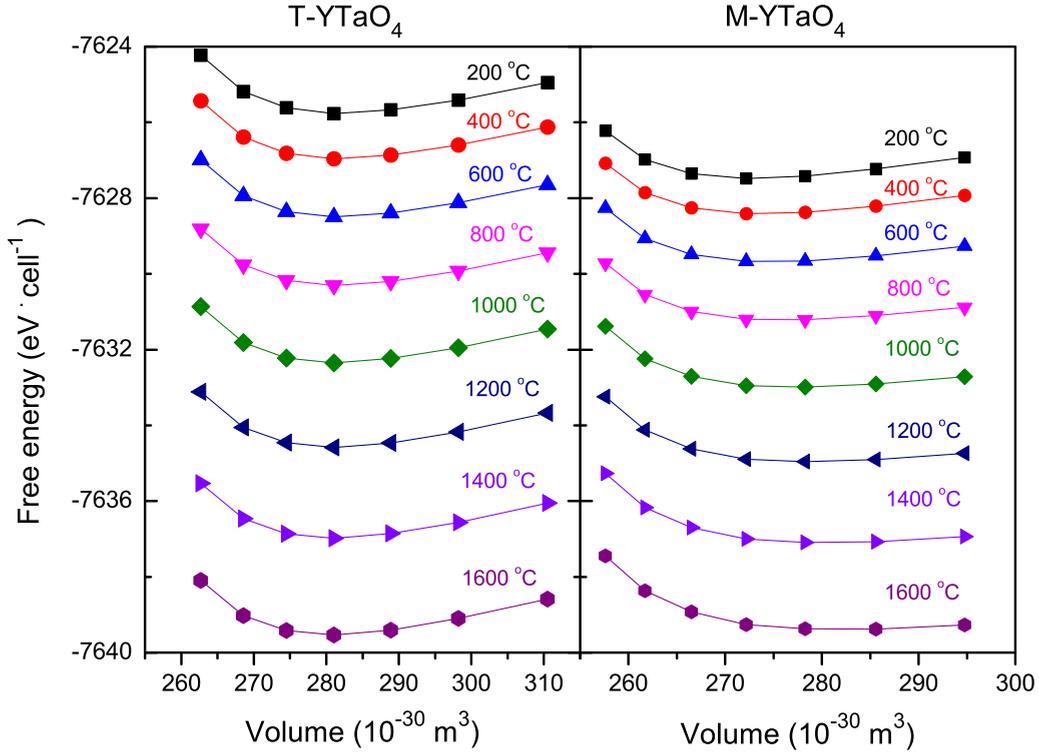


FIG. 3. (Color online) Volume dependence of the free energy of tetragonal and monoclinic phases of YTaO_4 from 200 to 1600 °C at 200 °C intervals calculated using the GIBBS code [36]. The solid symbols are calculated values and the solid lines are the fittings using the Birch-Murnaghan equation of states.

However, further refinement, in the form of anharmonic theory, is required to describe the physical properties at elevated temperatures. The properties of phonons were described using a harmonic approximation based on the knowledge of just the wave vectors and the frequencies $\omega(\mathbf{q})$, and polarization vectors $\mathbf{u}_k(\mathbf{q})$ of phonons with wave vectors \mathbf{q} are determined by the diagonalization of the dynamical matrix [41]:

$$\mathbf{D}_{kk'}^{\alpha\beta}(\mathbf{q}) = \frac{1}{\sqrt{m_k m_{k'}}} \sum_i \Phi_{kk'}^{\alpha\beta}(0l) \exp[-i\mathbf{q} \cdot (\mathbf{x}_0 - \mathbf{x}_l)], \quad (20)$$

which satisfies the eigenvalue equation

$$\sum_{k'} \mathbf{D}_{kk'}(\mathbf{q}) \mathbf{u}_{k'}(\mathbf{q}) = \omega^2(\mathbf{q}) \mathbf{u}_k(\mathbf{q}). \quad (21)$$

Here an infinite crystal is divided up into primitive cells (labeled by l) each containing r atoms (labeled by k) with ionic mass m_k . The real space interatomic force constants $\Phi_{kk'}^{\alpha\beta}(0l)$ include ionic and electronic contributions, so

$$\Phi_{kk'}^{\alpha\beta}(0l) = \Phi_{kk'}^{\alpha\beta}(0l)_{\text{ion}} + \Phi_{kk'}^{\alpha\beta}(0l)_{\text{el}}. \quad (22)$$

The ionic contribution is calculated from the Ewald sums and the electronic contribution can be expressed as

$$\Phi_{kk'}^{\alpha\beta}(0l)_{\text{el}} = \int \left[\frac{\partial \rho(\mathbf{r})}{\partial u_{\kappa}^{\alpha}(0)} \frac{\partial V_{\text{ion}}(\mathbf{r})}{\partial u_{\kappa'}^{\beta}(l)} + \rho(\mathbf{r}) \frac{\partial^2 V_{\text{ion}}(\mathbf{r})}{\partial u_{\kappa}^{\alpha}(0) \partial u_{\kappa'}^{\beta}(l)} \right] d^3r, \quad (23)$$

where $\rho(\mathbf{r})$ is the electron density, $V_{\text{ion}}(r)$ is the ionic potential, and $\partial \rho(\mathbf{r}) / \partial u_{\kappa}^{\alpha}(0)$ represents the density response of the

system to a displacement of the k atom in the reference cell ($l = 0$) along the α direction [41]. This linear electron-density response is applied self-consistently in DFPT.

The partial (or projected) phonon density of states was determined as a contribution from the given atom to the total phonon DOS. The contribution to the partial density of state on atom i , from each phonon band $N_i(E)$, was evaluated using

$$N_i(E) = \int \frac{d\mathbf{k}}{4\pi^3} |g_j(i)|^2 \Delta[E - E_n(\mathbf{k})], \quad (24)$$

where g_j is the eigenvector (normalized to unit length) associated with the mode of energy E_j . The projected density of states was then obtained by summation of these individual contributions over all phonon bands.

IV. RESULTS

A. Free energies

The Gibbs free energies calculated at constant pressure for the two YTaO_4 phases are shown as a function of temperature in Fig. 4(a). The transition temperature, determined by the intersection point of the two curves, was found to be 1430 °C. This is in excellent agreement with the recent *in situ* measurement of the transition temperature by high-temperature powder x-ray diffraction (1426 ± 7 °C) [42]. The crystal structures and atomic positions of the two YTaO_4 polymorphs were also obtained at different temperatures using the same method. The structural parameters determined at room temperature and 1475 °C for monoclinic and tetragonal phases are given in Table I. The volumes of the unit cells as a function of

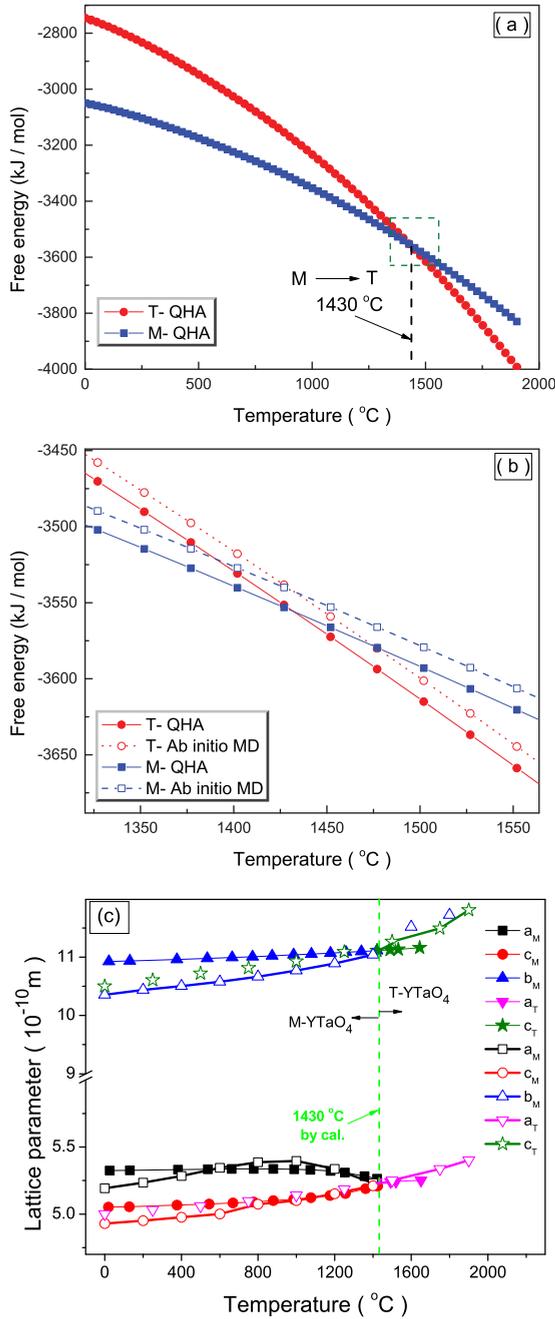


FIG. 4. (Color online) (a) The computed Gibbs free energies of the tetragonal and monoclinic YTaO₄ phases as a function of temperature. The intersection of the two curves indicates that the transition temperature is close to 1430 °C. As described in the text, the Gibbs free energy of T-/M-YTaO₄ compound was evaluated using Debye’s quasiharmonic approximation (QHA), as implemented in GIBBS code [36]. (b) Comparison of the free energies of the two phases calculated using the QHA and *ab initio* MD methods in the vicinity of the transition temperature. The differences in energy are small indicating that the anharmonic contribution to the total free energy of the two phases is also small. There is no discernible effect on the calculated transition temperature. (c) The calculated (open symbols) and measured (filled symbols) lattice parameters of the monoclinic and tetragonal YTaO₄ phases as a function of temperature. Note that the calculated transition temperature (1430 °C) agrees well with the experimental value (1426 ± 7 °C) [42].

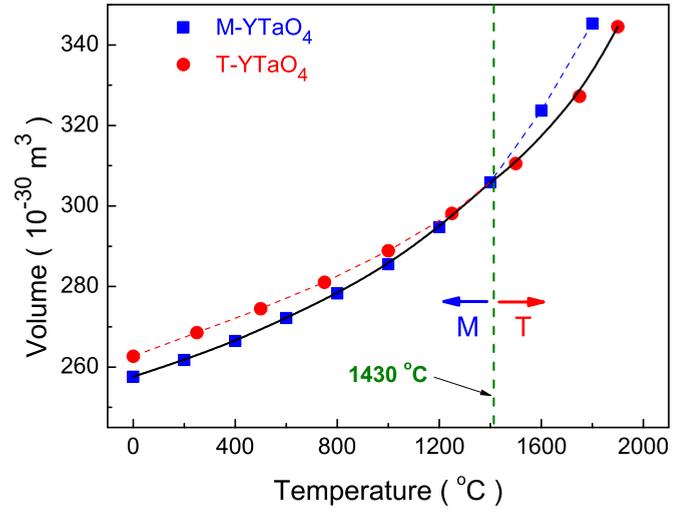


FIG. 5. (Color online) The calculated cell volume as a function of temperature of the M-YTaO₄ (blue squares represent low-temperature monoclinic phase) and T-YTaO₄ (red circles represent high-temperature tetragonal phase) phases. The dash and the solid lines represent the imaginary and the actual volumes, respectively.

temperature [Fig. 4(a)] indicate a continuous change in volume across the transition. The lattice constants of the two YTaO₄ phases were calculated in the QHA using the GIBBS code at different temperatures directly. These are compared in Fig. 4(b) with the values measured by x-ray diffraction at temperature and reported in Ref. [42]. The agreement between calculated values and experiments is satisfactory as shown in Fig. 4(c). Both the calculated and measured b_m exhibit the similar trend as temperature decreases below the transformation temperature. On the other hand, the calculated a_m and c_m are close to the measured values. Figure 5 shows the calculated cell volume as a function of temperature of the two phases. Note that the volume changes continuously during the phase transition, at least within the resolution of the simulation. The discrepancies between QHA calculations and x-ray diffraction measurements are attributed to a combination of errors in the QHA calculations and presence of lattice defects, such as vacancies and interstitials, which usually produce a larger lattice parameter than calculated.

B. Elastic constants

The calculated values of the 13 independent elastic constants are shown in Table II and these values were used to calculate the excess Gibbs free energy in Landau theory as described in the following section. Examination of the elastic constants (c_{11}^0 , c_{22}^0 , and c_{33}^0) indicate that the bonding in the [100] direction is stiffer than that in [010] and [001] directions for the monoclinic phase. Furthermore, the values suggest that the monoclinic phase is weakly anisotropic, whereas the tetragonal phase is much more anisotropic. These anisotropies can be expressed in terms of the recently proposed universal anisotropic indices (A^U) [43]. The anisotropic index (A^U) for monoclinic is 0.445, typical of many simple oxides, whereas that of the tetragonal phase is 5.397 which is unusually high,

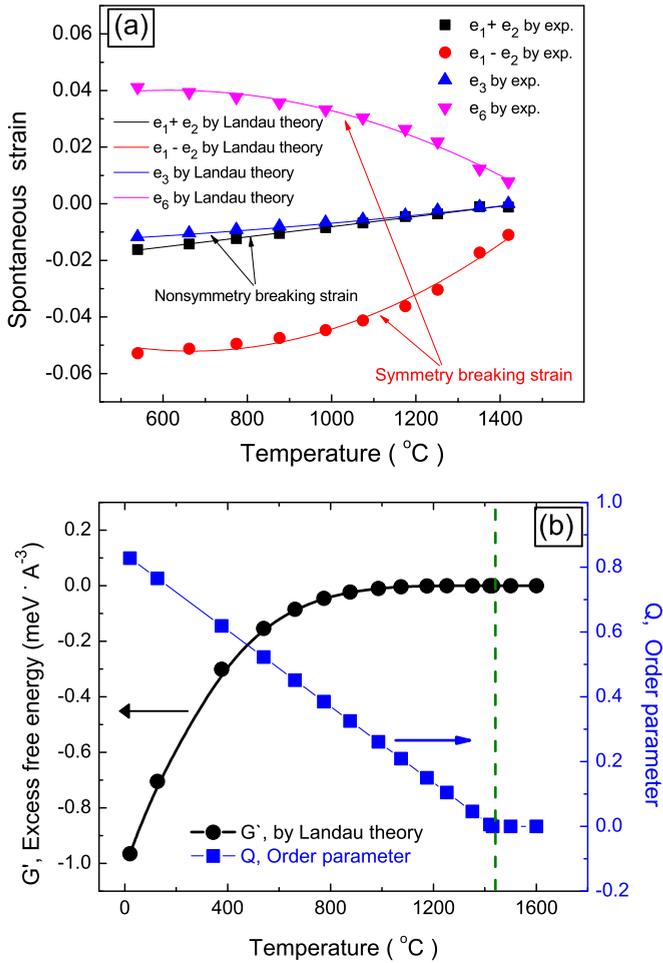


FIG. 6. (Color online) (a) The spontaneous macroscopic strains indicated by the symbols calculated using Eq. (2) with the experimental lattice constants from Ref. [42]. The solid lines represent the strains calculated from lattice constants from first-principles calculations. (b) The Landau excess free energy and the corresponding square of order parameters Q are shown as a function of temperature. The dashed vertical line refers to the transition temperature.

at least compared with the crystals cataloged by Ranganathan and Ostojca-Starzewski [43].

C. Landau free-energy parameters

The macroscopic spontaneous strains were calculated using Eq. (1) based on the experimentally measured lattice parameters. The strains are shown in Fig. 6 indicating that the Landau model satisfactorily describes the ferroelastic transition in the YTaO₄ system as the calculated strains closely match the experimental values over a relatively wide range of temperatures, down to one half of the transition temperature (in Kelvin). Above the transition temperature, they all vanish

for the tetragonal YTaO₄ phase as expected. The Landau excess free energy and Q^2 for the monoclinic YTaO₄ are also calculated by finding the solutions to Eqs. (5)–(8) based on the values of the computed elastic constants and the coupling parameters (shown in Table III). The results are shown in Fig. 6(b). Furthermore, the square of the order parameter Q^2 , calculated using Eq. (12), increases linearly with temperature below T_c and is above the transition temperature.

D. Phonon spectra

At the lattice level, a ferroelastic transformation can be driven by the softening of either optical or acoustic modes lying in the Brillouin zone. The calculated phonon dispersion curves and the vibrational density of states of the tetragonal and monoclinic phase are shown in Fig. 7 for their ground states. Neither of the crystal structures in their reference state exhibits a soft mode for any wave vector. They are thus both stable structures, dynamically as well as energetically, in their reference states. On cooling below the transition temperature, however, soft modes appear in the phonon dispersion curves of the tetragonal phase. These are shown in Fig. 8 for three different temperatures below the transition temperature. Comparison of the phonon spectra near the transition temperature shows that the tetragonal-to-monoclinic phase transition is caused by the softening of the two transverse acoustic modes in the zone center. These are shown in greater detail in Fig. 9(a) at the transformation temperature and three lower temperatures for comparison. The vibration pattern is illustrated in Fig. 9(b) for the first soft-acoustic modes at the BZ center with symmetry E_u in the [001] direction. By analyzing the eigenvectors for the soft mode, we find that all the atoms in the crystal structure are simultaneously displaced either in the [001] direction or the [100] direction. We find that for the tetragonal phase, the softening of transverse acoustic mode in the [001] direction leads to an elastic instability associated with shear elastic constants c_{44}^0 and c_{66}^0 . Meanwhile, the softening of transverse acoustic mode in [100] direction corresponds to the instability of c_{66}^0 . However, our calculations reveal that the elastic instability of tetragonal YTaO₄ below the transition temperature is initiated by the softening of c_{66}^0 , which is negative below T_c , since the constant c_{44}^0 remains positive for all the temperatures. The acoustic phase velocities determined near the Gamma point in the phonon spectra of Figs. 7 and 9 [44] were used to compute the elastic constants with the transverse acoustic (shear waves) corresponding to the constants $c_{44}^0, c_{55}^0, c_{66}^0$ and longitudinal acoustic waves corresponding to the constants $c_{11}^0, c_{22}^0, c_{33}^0$. Above the transition temperature, all the elastic constants of the tetragonal structure are positive.

In general, a good agreement is found between calculated Raman frequency and experimentally measured spectra for the monoclinic phase (Fig. 10 and Table IV) [45]. Similar agreement has been reported for the cubic-tetragonal-monoclinic

TABLE III. Parameters used in Landau theory for tetragonal to monoclinic YTaO₄ phase transition.

Parameter	a'	b'	b^*	λ_1	λ_2	λ_3	λ_4
Value	0.004 243	8.2854	8.2155	12.272	13.8325	-0.00 015	0.000 454

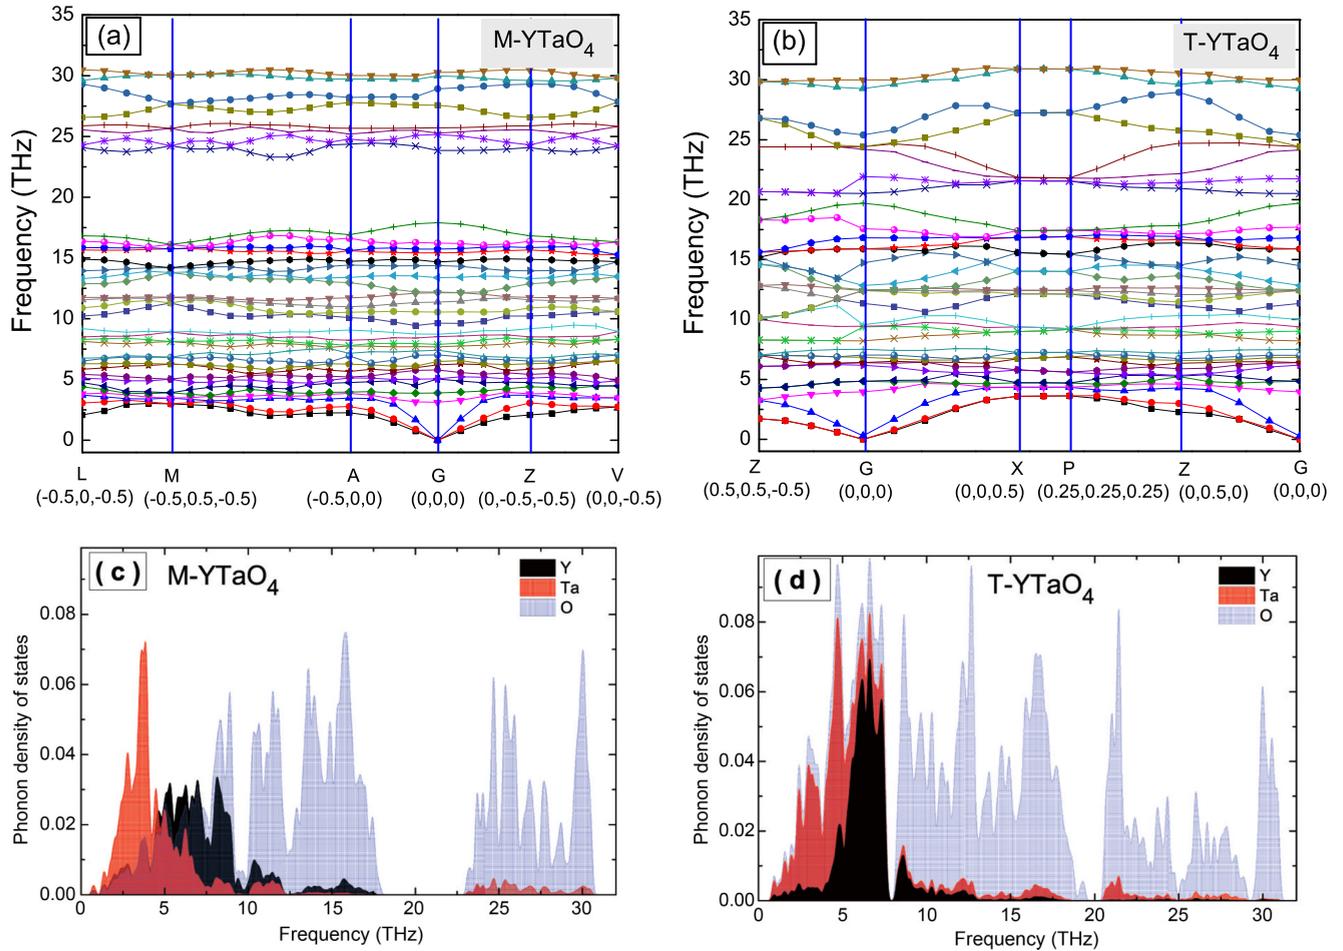


FIG. 7. (Color online) The phonon dispersion curves and the density of states of the ground states of the monoclinic and tetragonal phases.

phase transition in ScVO_4 [15]. During the tetragonal to monoclinic transition, each E_g mode splits into two B_g modes. Moreover, the A_g and B_g modes in the high symmetry, tetragonal phase are predicted to convert to other modes with A_g symmetry in the monoclinic phase. Our observations, up to 1000 °C, show that peaks associated with the two B_g modes of monoclinic phase approach one another but the thermal background above that temperature prevented us from making unambiguous peak identifications. Therefore, the softening in the B_g mode could not be conclusively verified.

E. Bond population in phase transition

The evolution of the relevant Ta-O and Y-O bond's population is collected in Fig. 11. Despite the Ta atoms having the same notional fourfold coordination in both the scheelite and fergusonite structures, an analysis of the Ta-O distances across the transition shows that the single Ta-O bond in the tetragonal structure splits into two different Ta-O bonds. The changes in lengths of the bonds are tiny but reproducible [13]. Similar results are also identified from the bond population in phase transition by the Mulliken analysis method as shown in Fig. 11. It shows the Ta-O bonds are more covalent and Y-O bonds more ionic in the crystal structure of YTao_4 .

V. DISCUSSION

Our calculations demonstrate that the transition between the high-temperature tetragonal phase of YTao_4 and the lower temperature, monoclinic polymorph is consistent with the transition being a second-order, ferroelastic transition and that the underlying mechanism is associated with phonon softening. The predicted lattice parameters and transformation temperature, as well as the temperature dependence of the symmetry-breaking strains, are all in good agreement with recent measurements providing confidence in the accuracy of the other predictions, such as the identity of the soft modes, the Raman spectra, and the elastic constants, that have not yet been determined by experiment. Further confirmation of the transition temperature was obtained by carrying out a series of molecular dynamics calculations of the free energies of the tetragonal and monoclinic phases in the vicinity of the transformation. The free energies, calculated using the Verlet algorithm in the CASTEP suite of programs, are shown in Fig. 4(b). As expected, the free energies are slightly higher on account of the anharmonic contributions to the energies but the transition temperature is unaffected.

Consistent with previous studies of ferroelasticity [11,14,23,26], we started by assuming that the appropriate form for the Landau free energy was that for a pseudoproper transformation, as shown in Eq. (4). This form allows for the

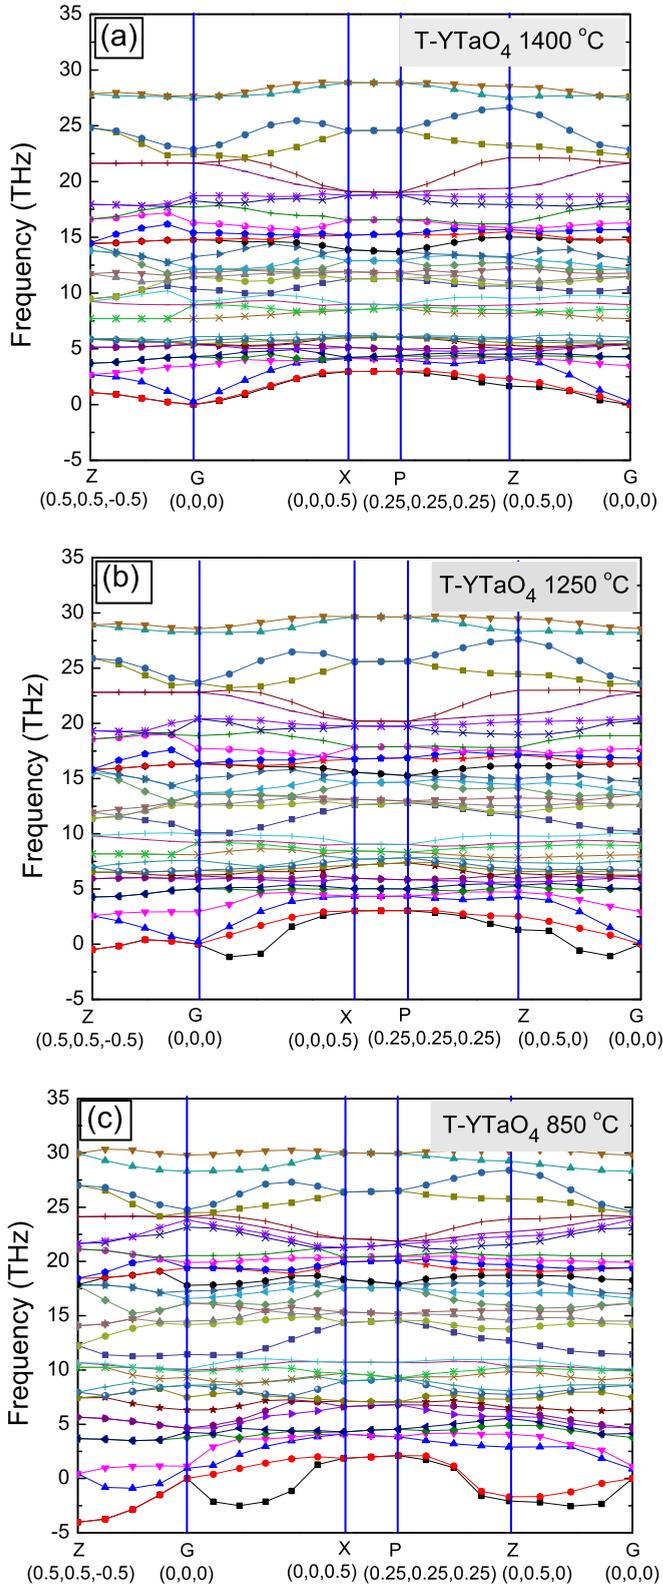


FIG. 8. (Color online) Phonon dispersion curves of tetragonal YTaO₄ at progressively low temperature, below the transition temperature: (a) 1400 °C, (b) 1250 °C, and (c) 850 °C. The soft modes are indicated by the negative values.

possibility of a structural parameter, such as the tilting of polyhedral structural units, to be represented by order parameter Q as the main driving force for the transformation. However, as seen in Table III, the calculated coupling parameters associated with the symmetry-breaking strains λ_3 and λ_4 are very small. Consequently, the calculated renormalized transition temperature T_c^* and coefficient b^* are essentially the same as T_c and b , respectively [Eqs. (11) and (12)]. These results could be mistakenly interpreted as the contributions of the symmetry-breaking strains to the Landau free energy are negligible. Rather, Q represents the symmetry-breaking strains, instead of other structural parameters. The equations compensate the redundant representation of symmetry-breaking strains by allowing the associated coupling parameters to be very small. We conclude that the transformation is a proper type, rather than pseudoproper. This conclusion is also in agreement with the phase transition occurring in both LaNbO₄ at 770 K [46] and DyVO₄ [47] where the transformation from $4/m$ to $2/m$ is characterized as proper ferroelastic [21]. This is also consistent with our finding that the temperature dependent order parameter can be represented in terms of the spontaneous breaking strains [42].

The computed bond lengths also provide some insight into the structural changes observed. In the tetragonal phase, the positions of the cations are fixed by symmetry and the cations planes are spaced exactly by $c/4$, along the longest axis (Fig. 1). As a consequence, the cation polyhedra can only tilt to accommodate the expansion or contraction of the bond lengths during temperature changes. After transitioning to the monoclinic phase, however, both the Y and Ta polyhedra have an additional degree of freedom, and can translate along the b axis of the monoclinic (corresponding to the tetragonal c axis). This translational freedom allows the Y and Ta planes to move relative to one another as shown in the crystal structure of Fig. 12. At the same time, as the temperature decreases, the oxygen ions in the monoclinic phase become increasingly aligned in their closed-packed planes. Adjacent, closed-packed planes shear relative to one another, increasing the monoclinic angle with decreasing temperature below the transition temperature (Fig. 12). This suggests that the monoclinic angle can be used as an experimentally determinable order parameter. Indeed, our data for the monoclinic angle $\Delta\beta = \beta - 90$ shows a power law exponent of $1/2$ in accord with the Landau free-energy expansion down to about 700 °C [42].

The Mulliken population analyses clearly indicate the contrasting covalent nature of the Ta-O and the Y-O ionic bonding, which is not surprising. More revealing, however, is that the effective coordination number (ECN) of the cations changes during the transformation. Using a weighted sum scheme [48] in which the anions are counted as fractional numbers, from 1 for the nearest anion, decreasing to zero as the anion distance increases, the effective coordination number of the tantalum ions are 4.0 and 4.3, in the tetragonal and monoclinic phases, respectively. The effective coordination of 4.0 for the tantalum ions in the tetragonal phase corresponds to the notional coordination of Ta in a TaO₄ tetrahedron but the larger number in the monoclinic phase indicates that the TaO₄ tetrahedra are distorted. This is consistent with the calculations indicating that one pair of Ta-O bonds became elongated while the other pair contracts (Fig. 1). The latter, in turn, allows other nearby

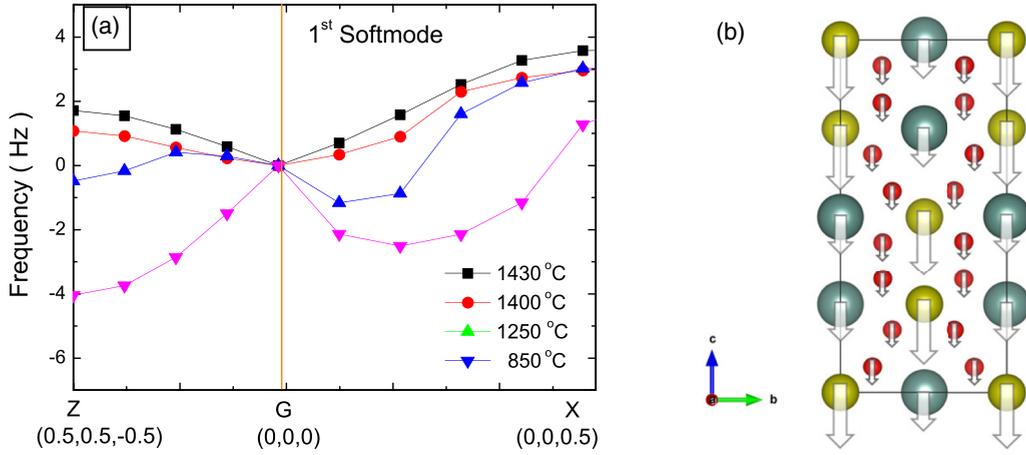


FIG. 9. (Color online) (a) The softening of one of the transverse-acoustic modes in the [001] direction of tetragonal phase near the center of the BZ at different temperatures. (b) The vibrational directions corresponding to the soft-transverse acoustic mode at the zone center with irreducible representation E_u . Note: All arrows point toward (0 0 -1) and their size indicate relative amplitudes of the vibration. The color and sizes of the atoms are the same as shown in Fig. 1.

oxygen atoms to move closer to the central Ta ion contributing to the slight increase in the coordination number. Essentially, the TaO₄ tetrahedra become less symmetric and more densely packed in the monoclinic phase than in the tetragonal phase. The effective coordination number of the yttrium ions only decreases slightly from 8.0 in the tetragonal phase to 7.92 in the monoclinic phases, which is probably not significant.

One of our findings is that the transformation is associated with a soft acoustic mode at the BZ center with a symmetry of E_u in the [001] direction. This contrasts with the B_g soft mode that has been reported for similar compounds, ScVO₄ [15], YVO₄ [49], BiVO₄ [50,51], and YNbO₄, which have the same space groups and point group, and which also undergo a tetragonal (scheelite) and monoclinic (fergusonite) transformation. As the radius, mass, and positions of the individual atoms, as

well as their local environment and symmetry, can all affect the vibrational energies, we also calculated the vibrational modes of YVO₄ and YNbO₄, again from first principles, and found that they have the B_g soft mode, consistent with previous reports. However, for the Yb analog, YbTaO₄, the transformation is associated with the A_u symmetry of an acoustic mode at the center of the Brillouin zone. A comparison of the energy ranges of the vibrational modes for the four

TABLE IV. The experimental (at room temperature) and the first-principles calculated (at 0 K) frequencies of Raman modes are shown for both monoclinic and tetragonal YTaO₄.

M-YTaO ₄					
Experiment			T-YTaO ₄		
Modes	(cm ⁻¹)	Intensity	Calc. (cm ⁻¹)	Modes ^a	Calc. (cm ⁻¹)
B_g	119 ^b	strong	109	$T(E_g)$	179
A_g	127	weak	133	$T(B_g)$	181
B_g	160	weak	171	$T(B_g)$	203
A_g	201	medium	207	$T(E_g)$	257
B_g	223	medium	238	$R(A_g)$	298
B_g	241	medium	251	$R(E_g)$	309
A_g	327	strong	307	$\nu_2(A_g)$	393
A_g	349	strong	346	$\nu_2(B_g)$	442
B_g	378	weak	367	$\nu_4(B_g)$	514
A_g	—	—	405	$\nu_4(E_g)$	591
B_g	427	weak	421	$\nu_3(E_g)$	625
B_g	457	weak	466	$\nu_3(B_g)$	749
B_g	487	weak	522	$\nu_1(A_g)$	—
A_g	531	very weak	529	—	—
	671	medium	—	—	—
	705	weak	—	—	—
A_g	825	strong	824	—	—
B_g	—	—	831	—	—
B_g	—	—	901	—	—
A_g	—	—	995	—	—

^aReference by Manjon [49].
^bMaybe cut off by laser filter.

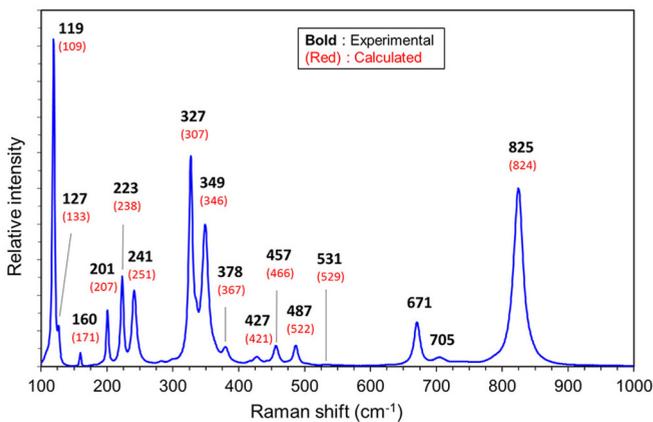


FIG. 10. (Color online) Room temperature Raman spectrum of monoclinic YTaO₄. The peak locations are determined by peak fitting (bold) and are compared with calculation (in parentheses and red) as shown in Table IV. In general, the calculated peaks locations are in good agreement with the experimental data, with the exception of the peaks located at 671 and 705 cm⁻¹. The laser excitation was 532 nm and the lowest energy peak at 119 cm⁻¹ may have been partially truncated by the laser filter.

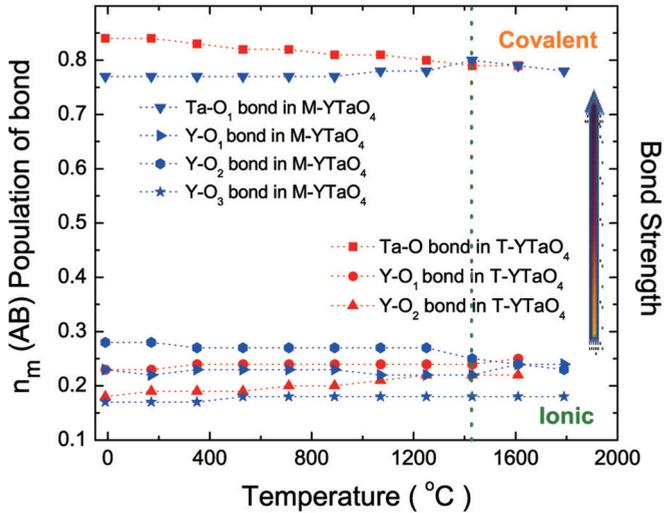


FIG. 11. (Color online) Population of the cation-oxygen bonds as a function of temperature for the tetragonal and monoclinic phases. The Ta-O and Y-O bonds have covalent and ionic characteristics, respectively, at all temperatures.

compounds with the fergusonite structure is listed in Table V. As can be seen from the energies of the allowable vibrational modes, summarized in the table, while the high energy modes of the four compounds have the same character, this is not the case when comparing the low energy modes. For these there is greater similarity between the compounds with the heavier, Ta ion in the B site, than with YNbO_4 . These differences cannot be explained in terms of ionic radii since the radius of Nb^{5+} and Ta^{5+} are almost identical in the same coordination but we note that tantalum has a higher atomic weight. Further work is

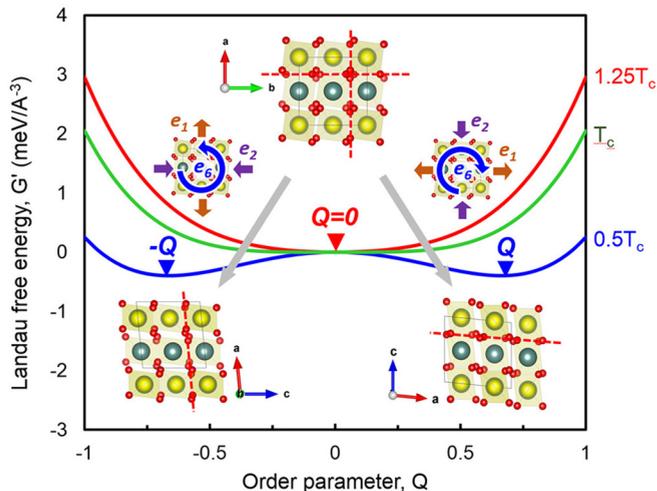


FIG. 12. (Color online) The Landau free energy G' as a function of order parameter Q plotted at different temperatures. The relation of the two monoclinic variant relative to the parent tetragonal phases and associated symmetry-breaking strains are also shown. Note the location of the unit cell and the orientation of closed-packed plane of oxygen (shown as dashed lines) in each monoclinic variant with respect to the parent tetragonal axis.

TABLE V. Comparison of the vibrational modes of compositionally related fergusonite ABO_4 compounds.

Energy range	YTao_4	YbTaO_4	YVO_4	YNbO_4
Low	E_u	A_u	B_g	B_g
Low	A_u	E_u	E_g	E_u
Medium	B_g	B_g	E_u	A_u
Medium	E_g	E_g	A_u	E_g
High	A_g	A_g	A_g	A_g
High	B_u	B_u	B_u	B_u

clearly needed to establish the reason for these differences in soft-mode behavior.

According to group theory the ferroelastic phase transition results in the formation of two equivalent variants of equal free energy. This can be seen from Eqs. (7) and (9), where the sign of symmetry-breaking strains $e_1 - e_2$ and e_6 change sign when the order parameter changes sign. The schematic diagram of the transitions along with the order parameter is shown in Fig. 12. In the parent tetragonal phase, the basal plane separation are equal in length (i.e., a and b) and the closed-packed oxygen planes are also equal in both the a or b directions. The first variant orientation occurs in response to the strains e_1 and $-e_2$ acting along the a and b axis of tetragonal, respectively, and the shear strain acting around the $-c$ axis. After the transformation, the tetragonal b axis becomes the c axis in the monoclinic and the resulting monoclinic structure has the closed-packed oxygen plane perpendicular to the tetragonal b axis. The orientation of the second variant emerges when the strains e_1 , $-e_2$, and e_6 operate in the opposite direction, i.e., along b and a axes, and around c axis of tetragonal, respectively, as illustrated in Fig. 12. Thus the tetragonal a axis becomes the c axis in the monoclinic and the closed-packed oxygen plane in the monoclinic structure is perpendicular to the tetragonal a axis. In the absence of any structural heterogeneity, both directions are equally favorable and consequently both monoclinic variants should exist at the same volume fraction. Since a and b are at the right angles, these monoclinic variants are consequently related by 90° rotation plus an offset determined by strain energy associated by the monoclinic deformation. This rotation can be clearly seen from the difference in the orientation of the closed-packed oxygen plane in each monoclinic variant. Additionally, opposite sides of the basal plane, i.e., c and a , should meet and therefore are strained at the boundary between the variants or domains. This analysis is supported by recent TEM observations of twin boundaries with rotational relation of 95.05° between the domains [42].

VI. CONCLUSIONS

First-principles calculations show that the tetragonal-to-monoclinic phase transition in the YTao_4 system is a second order, ferroelastic phase transition. The calculated transition temperature using first principles agrees well with the observed transition temperature recently reported by high-temperature x-ray diffraction. In addition, the Landau excess free energy for the monoclinic phase was derived from a “broken-symmetry” model of tetragonal YTao_4 . The calculated spontaneous

macroscopic strains using Landau's method also agree well with the experimental results. From the calculated phonon spectra, it can be concluded that the tetragonal-to-monoclinic phase transition is driven by the softening of transverse acoustic modes having E_u symmetry in the BZ center rather than the Raman-active B_g mode at the same \mathbf{k} point. The TaO₄ tetrahedra tilt produces not only a shearing to the monoclinic structure but also alters the separation of the cation planes in the c direction. Using a Mulliken analysis, the Ta-O bonds are predominately covalent and the Y-O bonds ionic. The Raman

modes in the tetragonal and monoclinic YTaO₄ have been calculated and, in general, there is a good agreement with experimental data for the monoclinic phase.

ACKNOWLEDGMENTS

This work was supported at Harvard University by a grant from ONR No. N00014-012-1-0993. We are indebted to Mary Gurak for making the Raman measurements.

-
- [1] E. Gregoryanz, R. J. Hemley, H. K. Mao, and P. Gillet, *Phys. Rev. Lett.* **84**, 3117 (2000).
- [2] E. Salje, *Annu. Rev. Mater. Res.* **42**, 265 (2012).
- [3] M. T. Dove, *Phase Transitions* **61**, 1 (1997).
- [4] E. K. H. Salje, S. A. Hayward, and W. T. Lee, *Acta Crystallogr. Sect. A* **61**, 3 (2005).
- [5] K. Aizu, *Phys. Rev. B* **2**, 754 (1970).
- [6] A. V. Virkar and R. Matsumoto, *J. Am. Ceram. Soc.* **69**, C224 (1986).
- [7] C. Mercer, J. R. Williams, D. R. Clarke, and A. G. Evans, *Proc. R. Soc. London Ser. A* **463**, 1393 (2007).
- [8] J. Chevalier, L. Gremillard, A. V. Virkar, and D. R. Clarke, *J. Am. Ceram. Soc.* **92**, 1901 (2009).
- [9] C. Chan, F. F. Lange, M. Rühle, J. Jue, and A. V. Virkar, *J. Am. Ceram. Soc.* **74**, 807 (1991).
- [10] D. Baither, M. Bartsch, B. Baufeld, A. Tikhonovsky, A. Foitzik, M. Rühle, and U. Messerschmidt, *J. Am. Ceram. Soc.* **84**, 1755 (2001).
- [11] M. A. Carpenter, R. J. Hemley, and H. K. Mao, *J. Geophys. Res.* **105**, 10807 (2000).
- [12] W. W. Cao, A. Saxena, and D. M. Hatch, *Phys. Rev. B* **64**, 024106 (2001).
- [13] N. Choudhury and S. L. Chaplot, *Phys. Rev. B* **73**, 094304 (2006).
- [14] A. Togo, F. Oba, and I. Tanaka, *Phys. Rev. B* **78**, 134106 (2008).
- [15] V. Panchal, F. J. Manjon, D. Errandonea, P. Rodriguez-Hernandez, J. Lopez-Solano, A. Munoz, S. N. Achary, and A. K. Tyagi, *Phys. Rev. B* **83**, 064111 (2011).
- [16] M. T. Dove and S. A. T. Redfern, *Am. Mineral.* **82**, 8 (1997).
- [17] M. Basta and A. Sieradzki, *Phase Transitions* **83**, 235 (2010).
- [18] J. A. Valgoma, J. M. Perez-Mato, A. Garca, K. Schwarz, and P. Blaha, *Phys. Rev. B* **65**, 134104 (2002).
- [19] S. Ono and K. Mibe, *Phys. Rev. B* **84**, 054114 (2011).
- [20] S. D. Gupta, S. K. Gupta, P. K. Jha, and N. N. Ovsyuk, *J. Raman Spectrosc.* **44**, 926 (2013).
- [21] E. K. H. Salje, *Phase Transitions in Ferroelastic and Co-elastic Crystals* (Cambridge University Press, Cambridge, 1990).
- [22] P. Toledano, M. M. Fejer, and B. A. Auld, *Phys. Rev. B* **27**, 5717 (1983).
- [23] M. A. Carpenter and E. Salje, *Eur. J. Mineral.* **10**, 693 (1998).
- [24] M. A. Carpenter, E. Salje, and A. Graeme-Barber, *Eur. J. Mineral.* **10**, 621 (1998).
- [25] G. Errandonea, *Phys. Rev. B* **21**, 5221 (1980).
- [26] D. Errandonea, R. Kumar, J. Lopez-Solano, P. Rodriguez-Hernandez, A. Munoz, M. G. Rabie, and R. S. Puche, *Phys. Rev. B* **83**, 134109 (2011).
- [27] V. S. Stubican, *J. Am. Ceram. Soc.* **47**, 55 (1964).
- [28] L. Jian and C. M. Wayman, *J. Am. Ceram. Soc.* **80**, 803 (1997).
- [29] L. Jian and C. M. Wayman, *J. Am. Ceram. Soc.* **79**, 1642 (1996).
- [30] G. Fadda, L. Truskinovsky, and G. Zanzotto, *Phys. Rev. B* **66**, 174107 (2002).
- [31] J. P. Perdew, K. Burke, and M. Ernzerhof, *Phys. Rev. Lett.* **77**, 3865 (1996).
- [32] J. D. Head and M. C. Zerner, *Chem. Phys. Lett.* **122**, 264 (1985).
- [33] M. D. Segall, R. Shah, C. J. Pickard, and M. C. Payne, *Phys. Rev. B* **54**, 16317 (1996).
- [34] S. Baroni, P. Giannozzi, and E. Isaev, *Rev. Mineral. Geochem.* **71**, 39 (2010).
- [35] A. Seko, F. Oba, A. Kuwabara, and I. Tanaka, *Phys. Rev. B* **72**, 024107 (2005).
- [36] M. A. Blanco, E. Francisco, and V. Luana, *Comput. Phys. Commun.* **158**, 57 (2004).
- [37] F. Birch, *Phys. Rev.* **71**, 809 (1947).
- [38] M. Segall, P. Lindan, M. Probert, C. Pickard, P. Hasnip, S. Clark, and M. Payne, *J. Phys.: Condens. Matter* **14**, 2717 (2002).
- [39] P. Hohenberg and W. Kohn, *Phys. Rev.* **136**, B864 (1964).
- [40] S. Baroni, S. de Gironcoli, A. Dal Corso, and P. Giannozzi, *Rev. Mod. Phys.* **73**, 515 (2001).
- [41] B. B. Karki, R. M. Wentzcovitch, S. de Gironcoli, and S. Baroni, *Phys. Rev. B* **61**, 8793 (2000).
- [42] S. Shian, P. Sarin, M. Gurak, M. Baram, W. M. Kriven, and D. R. Clarke, *Acta Mater.* **69**, 196 (2014).
- [43] S. I. Ranganathan and M. Ostoja-Starzewski, *Phys. Rev. Lett.* **101**, 055504 (2008).
- [44] M. S. Kushwaha, P. Halevi, G. Martinez, L. Dobrzynski, and B. Djafari-Rouhani, *Phys. Rev. B* **49**, 2313 (1994).
- [45] G. Blasse, *J. Solid State Chem.* **7**, 169 (1973).
- [46] L. H. Brixner, J. F. Whitney, F. C. Zumsteg, and G. A. Jones, *Mater. Res. Bull.* **12**, 17 (1977).
- [47] W. Rehwald, *Adv. Phys.* **22**, 721 (1973).
- [48] C. Ferraris, *Fundamentals of Crystallography*, 3rd ed. (Oxford University Press, Oxford, 2011).
- [49] F. J. Manjon, P. Rodriguez-Hernandez, A. Munoz, A. H. Romero, D. Errandonea, and K. Syassen, *Phys. Rev. B* **81**, 075202 (2010).
- [50] E. S. Fisher, *J. Phys.: Condens. Matter* **1**, 2875 (1989).
- [51] A. Pinczuk, G. Burns, and F. H. Dacol, *Solid State Commun.* **24**, 163 (1977).